

Pressure induced phase transitions in PbTiO_3 - a query for the polarization rotation theory

J. Frantti, Y. Fujioka and R. M. Nieminen

Laboratory of Physics, Helsinki University of Technology, P.O. Box 4100,
FIN-02015 HUT, Finland

Abstract

Our first-principles computations show that the ground state of PbTiO_3 under hydrostatic pressure transforms discontinuously from $P4mm$ to $R3c$ at 9 GPa. Spontaneous polarization decreases with increasing pressure so that the $R3c$ phase transforms to the centrosymmetric $R\bar{3}c$ phase at around 30 GPa. The first-order phase transition between tetragonal and rhombohedral phase is exceptional since there is no evidence for a bridging phase. The essential feature of the $R3c$ and $R\bar{3}c$ phases is that they allow the oxygen octahedron to increase its volume V_B at the expense of cuboctahedral volume V_A around a Pb ion. This is further supported by the fact that neither the $R3m$ nor Cm phase, which keep the V_A/V_B ratio constant, is a ground state within the pressure range between 0 and 40 GPa. Thus tetragonal strain is dominant up to 9 GPa, whereas at higher pressures efficient compression through oxygen octahedra tilting plays the central role for PbTiO_3 . Previously predicted pressure induced colossal enhancement of piezoelectricity in PbTiO_3 corresponds to unstable Cm and $R3m$ phases. This suggests that the phase instability, in contrast to the polarization rotation, is responsible for the large piezoelectric properties observed in systems like $\text{Pb}(\text{Zr,Ti})\text{O}_3$ in the vicinity of the morphotropic phase boundary.

In ferroelectric crystals electric polarization occurs spontaneously. The spontaneous polarization occurs when the energy gained by the interaction of the dipoles induced by the local field is larger than the energy required to produce the dipoles [1]. This viewpoint was adopted once early attempts for explaining ferroelectricity were developed: the ferroelectric state is stable when the attractive dipolar energy exceeds the distortion energy. It soon turned out that the model in its simplest form was insufficient. For BaTiO_3 a phenomenological model, based on Slater's 'rattling' Ti ion and the fact that the environment of the oxygen ions is noncubic, was developed to explain ferroelectricity. A rattling Ti ion creates large ionic polarizability (implying small distortion energy), whereas the noncubic environment of oxygen ions

increases the local field contribution from the titanium. A large local field implies large dipolar attraction energy dominating over the distortion energy. Quantitative treatment of ferroelectricity in BaTiO_3 and PbTiO_3 was provided by first principles computations which, instead of a rattling titanium ion, considered the hybridization between Ti $3d$ and oxygen $2p$ states [2]. These computations were able to explain the difference between the zero pressure ground states of BaTiO_3 (rhombohedral) and PbTiO_3 (tetragonal) by considering Ba essentially as a closed shell ion and taking the hybridization of Pb $6s$ and oxygen $2p$ states into account. The ground state is very sensitive against primitive cell volume and one may expect significant changes in the structure of PbTiO_3 as a function of hydrostatic pressure. Recent development on ferroelectrics are due to the density functional theory (DFT) which provides an accurate value for the total energy except for the errors due to the approximate forms used to describe the exchange-correlation functional.

We used the ABINIT DFT code to compute the total energies at different pressures [3]. The computations were carried out within the local-density approximation (LDA) approximation and a plane wave basis. Norm-conserving pseudo-potentials (scalar-relativistic for Pb and non-relativistic for Ti and O [4]) were generated using the OPIUM pseudopotential generator package [5]. The valence states included $5d6s6p$ (Pb), $3s3p3d4s4p$ (Ti) and $2s2p3d$ (O) states. The energy cutoff was 75 hartree and the k -point meshes were $6 \times 6 \times 6$, except for the $R3c$ and $R\bar{3}c$ symmetries, for which it was $4 \times 4 \times 4$ (due to the larger primitive cell), and $I4cm$ symmetry, for which a mesh $6 \times 6 \times 4$ was used. Denser k -point meshes were used for computing spontaneous polarization through Berry's phase method. Structural optimization was carried out till force acting on each atom was below 5×10^{-6} eV/Å. Phonon frequencies and the corresponding atomic displacements (eigenvectors) were computed through response function method implemented in ABINIT. To tackle the problem of structural optimization we selected various potential crystal symmetries for which the enthalpies were computed as a function of pressure. Thus, due to the polarization rotation theory [6] the case where the Cm symmetry bridges the tetragonal $P4mm$ and rhombohedral $R3m$ symmetries is a particularly attractive possibility to be examined. The Cm phase is a common subgroup of the $P4mm$ and $R3m$ according to the group-subgroup chains $P4mm \rightarrow Cmm2 \rightarrow Cm$ and $R3m \rightarrow Cm$. In such a case a large electromechanical coupling coefficient, assigned to the Cm phase, was predicted [7]. This was based on the idea that the Cm phase would allow energetically favourable continuous rotation of polarization between the $[001]$ ($P4mm$ phase) and $[111]$ ($R3m$ phase) directions. At higher pressures the $R3m$ phase was proposed to transform to a cubic $Pm\bar{3}m$ phase. By symmetry, these phases do not possess octahedral tiltings: the role of the Cm phase is to be an energetically favourable path between the $P4mm$ and $R3m$ phases. An alternative path is a commensurate transition involving octahedral tiltings, which are frequently observed in oxide perovskites. This was suggested to occur also in PbTiO_3 under high pressure according to the phase

transition sequence $P4mm \rightarrow I4cm \rightarrow I4/mcm \rightarrow I4cm$ [8]. The proposed octahedral tilt system is the same as is found in SrTiO_3 . However, octahedral tilting is also found in rhombohedral $R3c$ and $R\bar{3}c$ phases. The $R3c$ space group is a generic rhombohedral symmetry in the sense that it allows both octahedral tilting and cation displacements. Thus, it is important to consider both $R3m$ symmetry (only cation displacements are allowed) and its subgroup $R3c$. The latter symmetry corresponds to the case where the two oxygen octahedra of the primitive cell are tilted about the pseudocubic [111] direction. The study of phonon instabilities provides invaluable information: particularly the phonon frequencies at the high symmetry points of the Brillouin zone and the acoustical branch provide very useful information related to the possible phase transitions. The first mentioned case provides information about commensurate phase transition whereas the incommensurate phase is signalled by a dip in the lowest frequency acoustical phonon branch. An incommensurate phase often bridges phases which do not possess group-subgroup relationship.

Figure 1 shows the enthalpies for $P4mm$, $Cmm2$, Cm , $I4cm$, $R3m$ and $R3c$ phases with respect to cubic $Pm\bar{3}m$ phase. As far as $P4mm$ and $R3m$ phases are concerned, it bears a close resemblance with the enthalpy curves given in ref. [7]. The difference between the enthalpies is very small except for the rhombohedral symmetries. This is due to the fact that also in the case of the Cm and $Cmm2$ symmetries the structural parameters turned out to correspond to the $P4mm$ though orthorhombic and monoclinic distortions were allowed. Neither orthorhombic nor monoclinic was energetically favourable as Figure 2 shows. Figure 1 reveals that the minimum enthalpy path corresponds to the phase transition sequence $P4mm \rightarrow R3c \rightarrow R\bar{3}c$. It is worth mentioning that, within the studied pressure range from 0 to 40 GPa, neither the Cm nor $R3m$ phase was a ground state although with increasing pressure the Cm phase became more favourable than $P4mm$ phase and the $R3m$ phase was more favourable than the Cm phase at even higher pressures. For the electromechanical properties it is crucial to note that the phase transition between the $P4mm$ and $R3c$ phases must be of first order and thus does not involve continuous polarization rotation. To put these observations on a firm ground phonon frequencies were computed at the high symmetry points of the Brillouin zone as a function of pressure. At zero pressure no phonon instabilities in the $P4mm$ phase were observed, consistently with experiments. However, once the pressure is increased the Brillouin zone corner (A point, $\mathbf{q} = (\frac{\pi}{a}\frac{\pi}{a}\frac{\pi}{c})$) B_1 mode becomes unstable at 10 GPa, Figure 3. By further increasing the pressure also the E symmetry mode becomes unstable at 13 GPa. No other instabilities or anomalies in acoustical branches were observed. Though the frequencies of the Brillouin zone centre $A_1(1\text{TO})$ and $E(1\text{TO})$ modes were decreasing with increasing pressure they frequencies remained finite at the whole pressure range. Figure 4 a shows the oxygen displacements in B_1 and E symmetry and the structural distortion following the condensation of both modes. This bears a close analogy

to the $Pm\bar{3}m \rightarrow R\bar{3}c$ phase transition observed in LaAlO_3 [9]. The fact that the B_1 mode becomes unstable first suggests that the phase transition may occur in two stages. The oxygen octahedral rotation corresponding to the condensation of the B_1 mode is depicted in Figure 4 b and is similar to the case observed in SrTiO_3 [9]. The second stage is shown by black arrows in Figure 4 a. However, the $I4cm$ symmetry did not correspond to the minimum enthalpy, Figure 1. This implies that either the stability range of $I4cm$ phase is very narrow or the phase transition between $P4mm$ and $R3c$ phase takes place without an intermediate phase. In the case of a first-order phase transition the frequencies of the unstable modes do not reach zero at the transition point. It is remarkable that the information provided by the phonon instabilities, most notably by the phonon eigenvectors, is perfectly consistent with the analysis based on enthalpies.

The V_A/V_B ratio decreases with increasing hydrostatic pressure in rhombohedral $R3c$ and $R\bar{3}c$ phases. The central role of the tilt angle of the octahedron about $[111]$ direction (ω) is neatly given by the expression $V_A/V_B \approx 6 \cos^2 \omega - 1$ [10]. This is related to the increasing octahedral tilting and is clearly an important mechanism for minimizing the enthalpy. This is seen by comparing Figures 1 and 5 a and noting that $R3m$ phase does not permit octahedral tiltings. Figure 5 b shows that spontaneous polarization decreases monotonically with increasing pressure. There is a discontinuous drop in spontaneous polarization at 9 GPa so that not only is the polarization direction changed abruptly but also the magnitude drops significantly. With increasing pressure the cation shifts diminish and a transition between the $R3c$ and $R\bar{3}c$ phases occurs at around 30 GPa, see Figure 1. At 30 GPa the cation shifts from the centrosymmetric positions are small, which suggests that the transition is continuous. These results mean that under high pressure PbTiO_3 does not minimize its enthalpy through polarization rotation but by tilting the oxygen octahedra. This has very important consequence for the piezoelectric properties: though the d_{15} constant has a clear maximum at the phase transition there is no dramatic enhancement of piezoelectric constants at the phase transition pressures, as Figure 5 c shows. This is in complete contrast to the predictions based on the polarization rotation theory [6, 7]: in the pressure range between 9 and 15 GPa significantly larger piezoelectric coefficients are seen in the case of the $R3m$ and $P4mm$ phases, which do not permit polarization rotation. We conclude that it is the phase instability which results in the large piezoelectric constants. In a classical piezoelectric $\text{Pb}(\text{Zr,Ti})\text{O}_3$ system an analogous situation occurs in the vicinity of the morphotropic phase boundary (MPB) where the Cm phase coexists with the $R3m$ phase (at room temperature) or $R3c$ phase (at low temperature)[11]. Our computations suggest that it is the phase instabilities of the $R3m$ and/or Cm phase(s) which is responsible for the large electromechanical coupling coefficients observed at MPB.

Experimentally this zero temperature phase transition sequence $P4mm \rightarrow R3c \rightarrow R\bar{3}c$ can be verified through neutron diffraction experiments. Neutron

diffraction allows oxygen positions to be precisely located and the superlattice reflections allow the identification of octahedral tiltings. In addition, Raman spectroscopy provides useful complementary information: all phases have very distinctive spectra. Since the transition between $R3c$ and $R\bar{3}c$ is likely to be continuous, Raman scattering data are especially valuable: the Brillouin zone centre normal modes (IR and R stand for the infrared and Raman active modes) of $R3c$ and $R\bar{3}c$ transform as the representations $5A_1(IR, R) \oplus A_2 \oplus 10E(IR, R) \oplus$ and $A_{2g} \oplus E_g(R) \oplus 4A_{1u} \oplus 5A_{2u}(IR) \oplus 9E_u(IR)$, respectively. Thus, the $R3c$ phase has 15 peaks (excluding accidental degeneracies) whereas $R\bar{3}c$ has only one peak.

Acknowledgments

This project was financially supported by the Academy of Finland (Project Nos 207071 and 207501). Finnish IT Center for Science is acknowledged for providing computing environment.

References

- [1] Levy, R. A. *Principles of Solid State Physics*; Academic Press: London, 1968.
- [2] Cohen, R. E. *Nature* **1992**, 358, 136.
- [3] Gonze, X.; Beuken, J.-M.; Caracas, R.; Detraux, F.; Fuchs, M.; Rignanese, G.-M.; Sindic, L.; Verstraete, M.; Zerah, G.; Jollet, F.; Torrent, M.; Roy, A.; Mikami, M.; Ghosez, Ph.; Raty, J.-Y.; Allan, D. C. *Comput. Mater. Sci.* **2002**, 25, 478. Gonze, X.; Rignanese, G.-M.; Verstraete, M.; Beuken, J.-M.; Pouillon, Y.; Caracas, R.; Jollet, F.; Torrent, M.; Zerah, G.; Mikami, M.; Ghosez, Ph.; Veithen, M.; Raty, J.-Y.; Olevano, V.; Bruneval, F.; Reining, L.; Godby, R.; Onida, G.; Hamann, D. R.; Allan, D. C. *Zeit. Kristallogr.* **2005**, 220, 558.
- [4] Grinberg, I.; Ramer, N. J.; Rappe, A. M. *Phys. Rev. B* **2000**, 62, 2311.
- [5] Rappe, A. M.; Rabe, K. M.; Kaxiras, E.; Joannopoulos, J. D. *Phys. Rev. B* **1990**, 41, 1227.
- [6] Fu, H.; Cohen, R. E. *Nature* **2000**, 403, 281.
- [7] Wu, Z.; Cohen, R. E. *Phys. Rev. Lett.* **2005**, 95, 037601.
- [8] Kornev, I. A.; Bellaiche, L.; Bouvier P.; Janolin, P.-E.; Dkhil, B.; Kreisel, J. *Phys. Rev. Lett.* **2005**, 95, 196804.
- [9] Lines, M. E.; Glass, A. M. *Principles and Applications of Ferroelectric and Related Materials*; Clarendon Press: Oxford, 2001.

- [10] Thomas, N. W.; Beitollahi, A. *Acta Cryst. B* **1994**, 50, 549.
- [11] Frantti, J.; Eriksson, S.; Hull, S.; Lantto, V.; Rundlöf, H.; Kakihana, M. *J. Phys.: Condens. Matter* **2003**, 15, 6031.

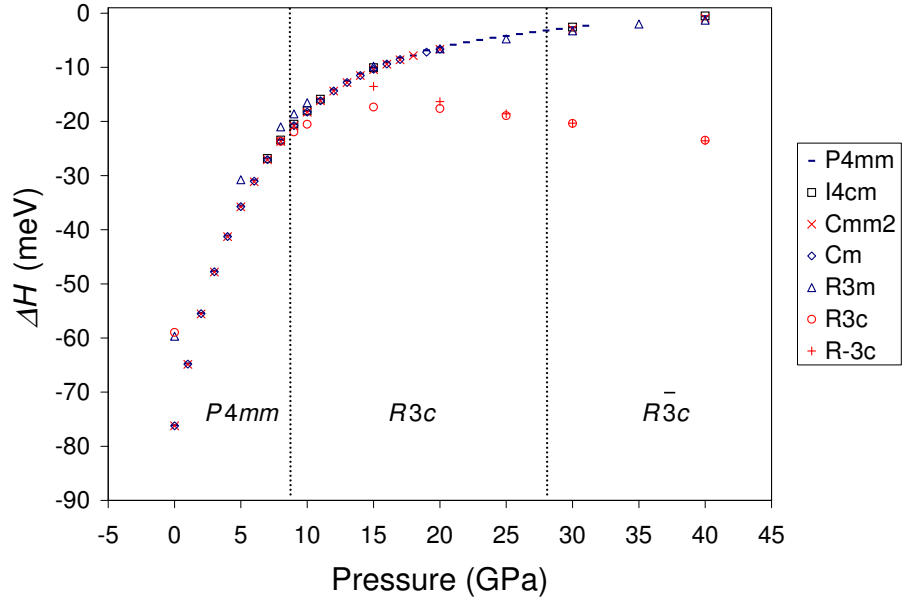


Figure 1: Enthalpies as a function of pressure with respect to the cubic $Pm\bar{3}m$ phase. Our first-principles computations reveal that energetically favourable and large crystal compression is allowed by tilting the oxygen octahedra. The minimum enthalpy path is $P4mm \rightarrow R3c \rightarrow R\bar{3}c$.

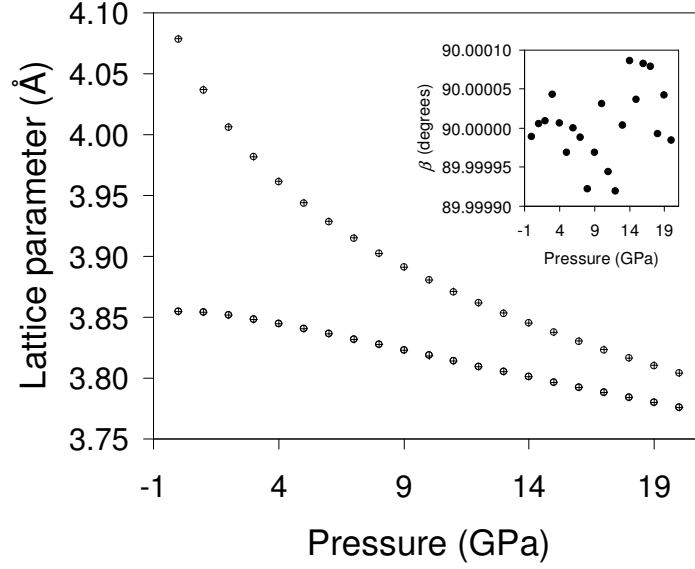


Figure 2: Lattice parameters for the $P4mm$ (crosses) and Cm (open circles) phases. For an easier comparison, the monoclinic a and b axes are divided by $\sqrt{2}$. Inset shows the behaviour of the monoclinic β angle as a function of pressure. It is seen that monoclinic distortion is essentially zero in the studied pressure range and thus PbTiO_3 has $P4mm$ symmetry up to 9 GPa at which a transition to the $R3c$ phase takes place.

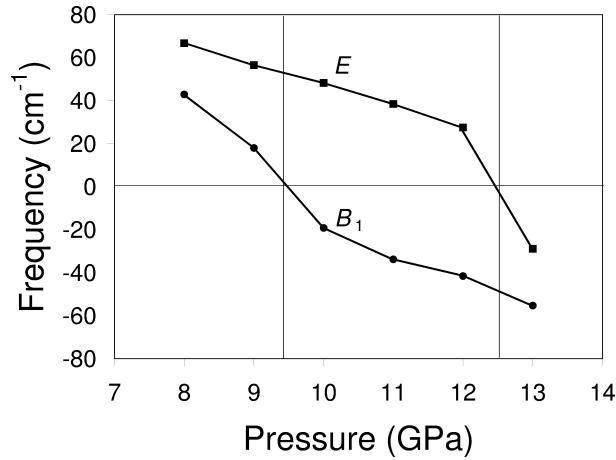


Figure 3: Brillouin zone boundary modes at A point ($\mathbf{q} = (\frac{\pi}{a} \frac{\pi}{a} \frac{\pi}{c})$) become unstable at 10 GPa (B_1 mode) and at 13 GPa (E symmetry mode). Lines are guides for the eyes.

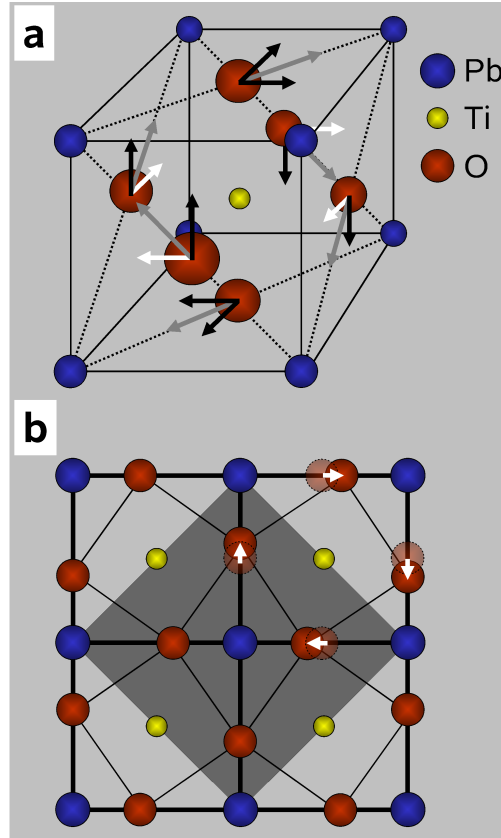


Figure 4: Phase transition between $P4mm$ and $R3c$ phases corresponds to the condensation of two modes. a, Oxygen displacements in two unstable modes corresponding to the Brillouin zone boundary A point. White and black arrows indicate the oxygen displacements in the B_1 and E symmetry modes, respectively. Grey arrows indicate the superposition of the B_1 and E symmetry modes resulting in rhombohedral symmetry (the shown octahedra is rotated clockwise and the next oxygen octahedra (not shown) along the $[111]$ direction is rotated anticlockwise). As a result of the condensation of these modes the symmetry discontinuously changes to a rhombohedral $R3c$ symmetry. b, Oxygen octahedral tilting in $I4cm$ phase. B_1 symmetry mode condensation corresponds to the phase transition between $P4mm$ symmetry and its subgroup $I4cm$. The ab basal plane of the $I4cm$ unit cell is indicated by dark grey shading.

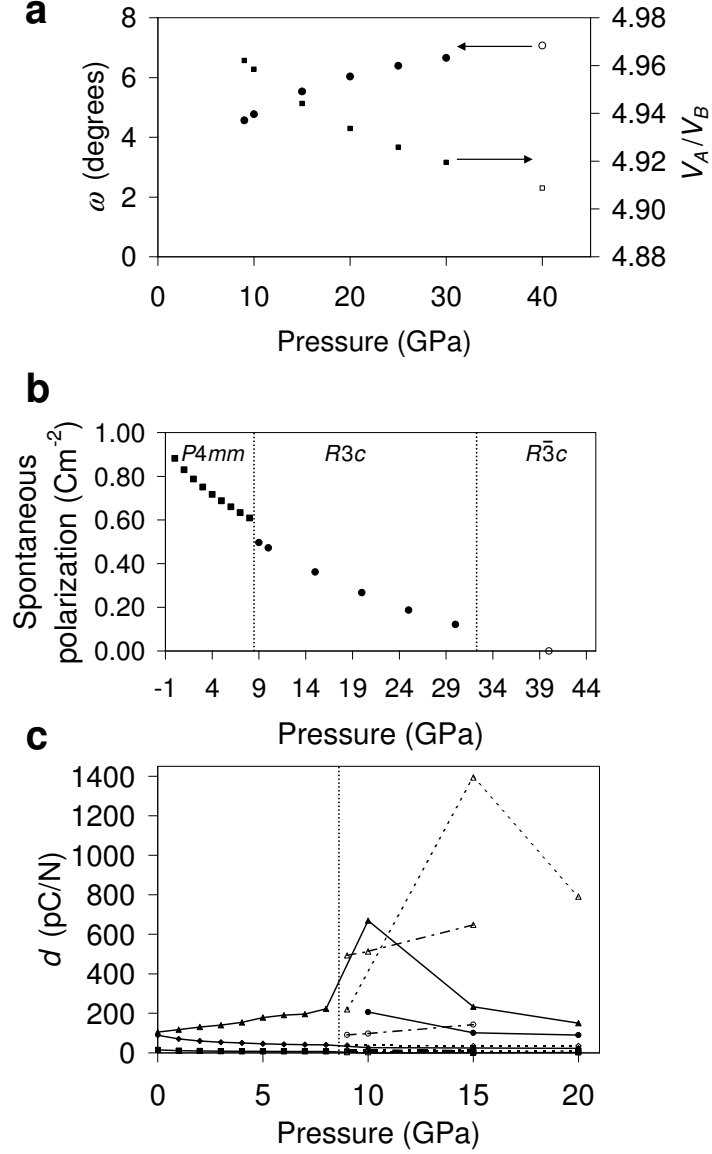


Figure 5: a, The ratio between cuboctahedra (V_A) and oxygen octahedra volume (V_B) as a function of pressure in $R3c$ (filled marks) and $R\bar{3}c$ (open marks) phases. The corresponding octahedral tilting angle ω is also shown. b, Spontaneous electric polarization across the proposed phase transition sequence. c, Absolute values of the piezoelectric constants for the stable phases (continuous line with filled symbols) and for the unstable phases ($P4mm$: dashed lines, $R3m$: dashed-dotted line). Squares, diamonds, triangles and spheres indicate d_{31} , d_{33} , d_{15} and d_{11} constants, respectively. The anomalously large d_{15} values of the $R3m$ and $P4mm$ phases at 15 GPa pressure are a clear indication of a structural instability. Symmetry dictates that for these phases polarization rotation is not possible and thus cannot offer an explanation for the anomaly.